

How to Choose the Right Coating for Fasteners

Q. I am being asked to specify metallic coatings for my company's fasteners. Can you provide some guidance for selecting a coating?

A. Though it is well known that coatings help with fastener performance by improving durability and lifespan, the importance of choosing the proper coating can often be overlooked. Common coating options for fasteners over a steel substrate include zinc, mechanical zinc, zinc-nickel, zinc-flake, tin-zinc and zinc-iron. Certain factors must be examined when choosing the appropriate coating to specify for your fastener application. It's always wise to begin with the end in mind. It's important to research and carefully consider the specific requirements of the fastener in its state of end use in order to determine the coating that will work best. Asking the right questions about factors such as corrosion resistance requirements, durability, temperature, torque tension needs, and more is the place to begin.

With a strong industry focus on corrosion resistance, let's start with a popular and helpful tool in considering the metallic layer to coat the steel substrate: the galvanic series seawater table (figure 1). The table provides the galvanic comparison of the various metals over steel, measured by electro potential volts. The farther apart the metals are on the chart, the more dissimilar they are, resulting in a higher potential for corrosion.

Starting at the top of the chart, we have aluminum, which is very active (anodic) compared to iron (our usual substrate) and at the bottom of the slide, we have gold, which is very noble (cathodic) to iron. Coatings that are more active than steel will protect the underlying substrate. These include zinc, cadmium, zinc-nickel and aluminum. Coatings that are more noble than steel will not be sacrificial to steel. These can include nickel, tin and copper.


To further this example, let's look at iron in the middle, highlighted in red. Directly above it is zinc-nickel 12%. The potential difference from iron to zinc-nickel is only 0.1 in the galvanic seawater series; if you compare that difference to iron/zinc, there is a 0.31 difference. This difference is what drives the corrosion rate of the sacrificial coating and should be one of the factors considered when identifying a coating choice for your fasteners.

The next factors we can delve into are durability and temperature requirements. Will the fastener be subject to abrasion and what temperature will it be exposed to? (For the purposes of walking through these examples, we are going to key in on zinc-nickel).

Zinc-Nickel has increasingly become the finish of choice for many industries with high corrosion and high-performance needs. From a durability standpoint, zinc-nickel has a Vickers Hardness of 400 to 500 HV (compared to a zinc-only deposit, which is approximately 100 HV). Because handling and assembly can be a destructive process for

Galvanic Series Seawater

Metal	E (Volts) at 25 C
Aluminum	-1.66
Zinc	-0.76
Zinc Ni (5-7% Ni)	-0.70
Cadmium	-0.60
Zinc Ni (12% Ni)	-0.55
Iron ++	-0.45
Nickel	-0.25
Tin	-0.14
Hydrogen	0.00
Copper ++	+0.34
Gold	+1.68

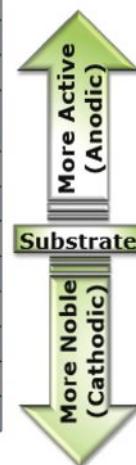

softer coatings like zinc and zinc flake, the combination of hardness and overall corrosion protection make the zinc-nickel alloy deposit ideal for fasteners or components that require further handling or assembly.

Another excellent benefit of the zinc-nickel alloy deposit is its overall resistance to heat. If your spec requires baking, the zinc-nickel deposit can withstand bake temperatures in excess of 200°C for four hours and still achieve 800 hours of neutral salt spray protection to first red rust. Zinc-nickel is commonly used on stampings and fasteners for barrel applications and heavily used on brake component castings in rack applications. Alkaline and acid zinc nickel offer different performance benefits that are suited to specific applications, so be sure to work with a knowledgeable chemistry supplier to select the appropriate process to meet your needs.

Hydrogen embrittlement is a primary concern for fastener manufacturers. Fasteners with Core Hardness over 39 HRC are susceptible to embrittlement from hydrogen. Fastener coatings should be selected to minimize risk, where coating risk is high, process should be validated that parts have not been embrittled. The porosity in the electroplated coating is a first order effect on hydrogen



MARK SCHARIO
Columbia Chemical

Executive Vice President for
Columbia Chemical.
Visit columbiachemical.com.